

RG 104, 8NS-104-94-077  
Box 6

8NS-104-94-077, Miscellaneous  
Correspondence & Memos, 1897-1994

Notes on Israeli Currency



ISREAL #1

.0945 = 560.

.093-.0935-EDGE


dia - 1.444-6

WT - 401.323 gms.

Israel #1





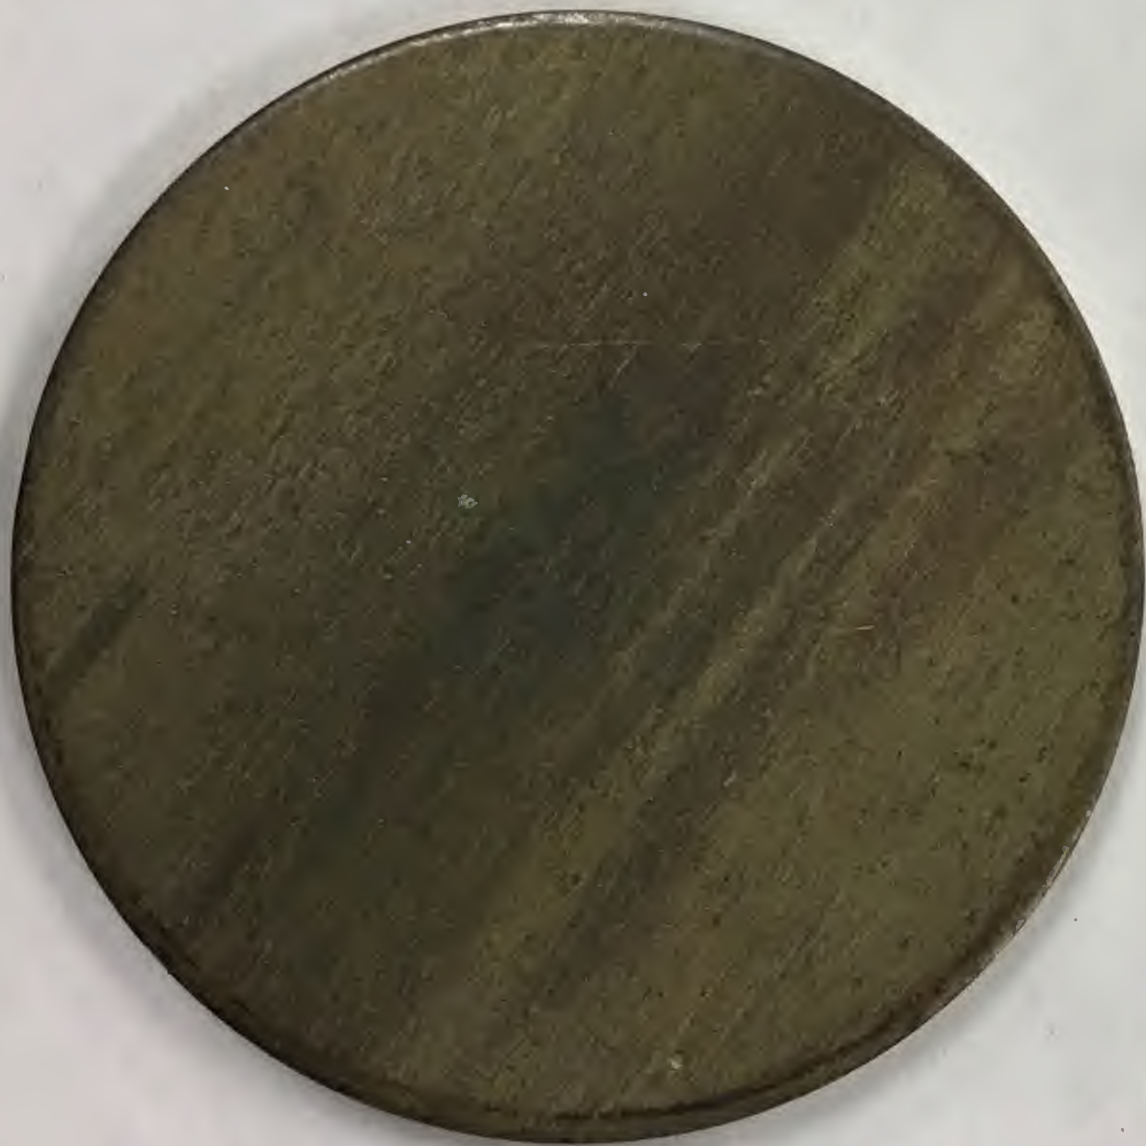

Hollinger Corp.  
pH 8.5



UNITED STATES GOVERNMENT

# Memorandum

*Rolling Room*

TO : Superintendents of Melting, Coining,  
Assay, and Mechanical Divisions

DATE: August 20, 1970

FROM : Cost Accounting Branch

SUBJECT: Job Numbers For Israel - Approximately 20,000 Blanks - 10 Pound  
Denomination

Melting

<u>Dept.</u>	<u>Charge</u>	
7700	7761	10 Pound Ingot

Process Weighing

<u>Dept.</u>	<u>Charge</u>	
8100	8161	10 Pound

✓ Rolling

<u>Dept.</u>	<u>Charge</u>	
7900	7961	10 Pound - Includes Rolling, Slab Annealing etc.

✓ Blanking

<u>Dept.</u>	<u>Charge</u>	
8200	8261	10 Pound

Selecting


<u>Dept.</u>	<u>Charge</u>	
8800	8861	10 Pound

Automatic Weighing

<u>Dept.</u>	<u>Charge</u>	
8400	8461	10 Pound

Counting

<u>Dept.</u>	<u>Charge</u>	
8700	8761	10 Pound-Bagging, Weighing





OFFICE OF  
DIRECTOR OF THE MINT

# THE DEPARTMENT OF THE TREASURY

WASHINGTON, D.C. 20220

August 14, 1970

RECEIVED

AUG 19 1970

OFFICE OF  
SUPERINTENDENT  
U. S. MINT AT DENVER

Mrs. Betty Higby  
Superintendent  
United States Mint  
Denver, Colorado 80204

Dear Mrs. Higby:

You are authorized to manufacture and ship to the San Francisco Assay Office approximately 20,000 blanks for Israel coinage. The blanks are to be 900 fine silver, gauge .095 inches and diameter 1.440 inches.

Sincerely,

*Mary Brooks*

Mary Brooks  
Director of the Mint

8-20-70

Charge Number

Rolling & Blitting 7961

Punching 8261

Diameter 1.445

Thickness .0945

Weight 401.323 oz +/- 6 grains

✓ Copy to: Chas. M.  
Bauer  
Acting





Rolling  
825<sup>3</sup> - R

825<sup>3</sup> - B

Annular  
Sept 8300  
8353

Upside 8553

Stamp. 8653

Israel

900 fine silver  
1st - .092 thickness

17128.90 gms

1.456 dia  
→ 401.323 gms ± 4

Standard .0935 thickness

2nd

New - 11-25-69

1.440 Dia

std = .0955 thickness

.095, 4 gr. later

.097 5 gr. later

edge = .0945

± or - 6 grams

WT. 401.323

Port  
Bag

3rd

New. 5-670

Dia. 1.444 Dia

std = .0945

WT 401.323 grams ± or - 6 grams

401.323

# Israel

- .094  $\frac{1}{2}$  Heavy  $3\frac{1}{2}$  + Grain
- .094 Heavy  $1\frac{1}{2}$  Grain
- .093  $\frac{1}{2}$  Standard
- .093  $\frac{1}{4}$  -  $\frac{1}{4}$  Grain
- .093 -  $1\frac{1}{4}$  Grain
- .092  $\frac{1}{2}$  -  $3\frac{1}{2}$  + Grain



R. R.

ISRAEL DOLLARS

Ingots

6 - 900 Fine Silver @ 6800 ounces each

Cut Blanks

Weight 401.323 Grains  $\pm$  6 Gr.

Diameter 1.444+

Thickness .0945

Weight of Cut Blanks Recovered 26,072 90

Weight of Cut Blanks Shipped 20,933 60

Percent of Cut Blanks Recovered 66.6%

Total Number of Pieces Shipped 25,000

Two Bags Per Box - Box Banded

Box Size (Inside Dimensions) 6"X10 3/4"X11 3/4"

Size of Thimble 1.446

Size of Punch 1.439

REMARKS: Cut Blanks were washed

## ISRAEL DOLLARS

Ingots                    6 - 900 Fine Silver @ 6800 ounces each

## Cut Blanks

Weight            401.323    Grains <sup>+</sup> - 6 Gr.

Diameter            1.444+

Thickness            .0945

Weight of Cut Blanks Recovered                    26,072 90

Weight of Cut Blanks Shipped                    20,933 60

Percent of Cut Blanks Recovered                    66.6%

Total Number of Pieces Shipped                    25,000

Two Bags Per Box - Box Banded

Box Size (Inside Dimensions)                    6"X10 3/4"X11 3/4"

Size of Thimble                    1.446

Size of Punch                    1.439

REMARKS:    Cut Blanks were washed



36.7 mm 5-6-70

1. 4 4 4-6 Dia  
.094 - 3gr Die

Israel

.094<sup>3/4</sup> - std

.096 - 5gr. #1

checked Die

1.440.2 1.440.3

3m x 25.4

1444

$$25.4 \overline{) 36.7400}$$

254

1130

1016

1140

1016

1240

1016

224

4 ingots

Terak  
900

1.440

dia.

.0955<sup>std.</sup>  
guage

---

11-24-69

Isreal \$1  
25,000 Pcs

6 Ingots  
Silver

Pia 1.444  
thickness .094



7974

— ISREAL — ~~8253~~ - 8261

DIAL GAUGE X-RAY

1 - ~~5~~ = .210

2 - 225 - .190

ANNEAL

3 - 195 - .140

4 - 180 - .120

5 - 170 - .110 — 584 -

6 - 165 - .098 — 550 -

7 - 163 - .093 1/2 — 529 - 534

CB - 3/4

NEW - 5-5-70

5-6-70 { .094 3/4  
 OK Dia - 1.444-6  
 edge .094 3/4  
 edge .0935

Wt. = 401.323 grs

Dia. = 1.456

.093 - 3/4

.0935 - 5/16

.094 - 1 1/2 grs

.095 +

1.440. new - 11-25-70

edge .0945

Rec @ 710

ISREAL - 81

9-23-70

90% AS

Pass

Dial

Gauge

X-RAY

225

.190

ANNEAL

195

.140

180

.120

170

.110

165

.098

163

.0945

534

550

584

EDGE - .0935 CENTER - .095

DIA - 1.444-6

WT - 401.323 grs.

ISRAEL TEN POUND

DATE COMPLETED	September 24, 1970
INGOTS USED	5 900 Fine Silver @ 6800 Oz. Per Ingot
WEIGHT OF CUT BLANK	401.323 Grains $\pm$ 6 Grains
DIAMETER OF CUT BLANK	1.444
THICKNESS OF CUT BLANK	.0945
WEIGHT OF CUT BLANKS Recovered from blanking	20,214 Oz.
WEIGHT OF BLANKS RECOVERED After reviewing which was shipped	16,872.55
PERCENT OF BLANKS Recovered after reviewing	83%
SIZE OF PUNCH THIMBLE	1.445
WIDTH OF STRIP	6 Inches
REMARKS:	
This shipment was to replace previous shipment that San Francisco rejected because blanks were pitted too bad for Proof Coins.	
Blanks were reviewed carefully after washing and the blanks shipped looked very good.	
Scrapped half of one strip because of pits.	



# Notes on Israeli Currency

1000 = 1000  
1000 = 1000

